

# COLD WORK STEELS

## Available Product Variants

Long Products

## Product Description

BÖHLER K888 MATRIX - This MATRIX steel offers an excellent combination of high toughness and high compressive strength. MATRIX materials have high toughness, which is a critical factor in many applications. However, the hardness achievable with commonly used MATRIX steels often limits the potential applications. BÖHLER K888 MATRIX breaks through this barrier and offers the best of both worlds of matrix steels and high alloy tool steels. BÖHLER K888 MATRIX is a unique problem solver in situations where high compressive strength and toughness are required. Its advantageous tempering behavior with a pronounced secondary hardness maximum also enables the use of advanced coatings.

## Process Melting

Powder metallurgy

## Properties

- > Toughness & Ductility : very high
- > Hardness : very high
- > Compressive strength : very high
- > Machinability : very high
- > Dimensional stability : very high

## Applications

- > Fine Blanking, Stamping, Blanking
- > Powder Pressing
- > General Components for Mechanical Engineering
- > Standard Parts (Molds, Plates, Pins, Punches)
- > Cold Forming
- > Pill punching dies
- > Machine knife (for producers)
- > Coining
- > Rolling
- > Components for Recycling Industry

## Technical data

Material designation	
BÖHLER patent	Market grade

## Chemical composition (wt. %)

C	Si	Cr	Mo	V	W	Co
0.60	0.85	4.40	2.80	1.10	2.45	3.80

**Material characteristics**

	Compressive strength	Dimensional stability during heat treatment	Toughness	Wear resistance abrasive	Wear resistance adhesive
<b>BÖHLER K888</b> <b>MATRIX</b>	★★★★	★★★★★	★★★★★	★★	★★
<b>BÖHLER K110</b>	★★	★★★	★	★★★	★★
<b>BÖHLER K294</b> <b>MICROCLEAN</b>	★★★★★	★★★★★	★★★	★★★★★	★★★★★
<b>BÖHLER K340</b> <b>ISODUR</b>	★★★	★★★★	★★★	★★★	★★★★
<b>BÖHLER K346</b>	★★★	★★★	★★★	★★★★	★★
<b>BÖHLER K353</b>	★★	★★★	★★	★★	★★
<b>BÖHLER K360</b> <b>ISODUR</b>	★★★	★★★★	★★★	★★★★	★★★★
<b>BÖHLER K390</b> <b>MICROCLEAN</b>	★★★★★	★★★★★	★★★★	★★★★★	★★★★★
<b>BÖHLER K490</b> <b>MICROCLEAN</b>	★★★★	★★★★★	★★★★	★★★★	★★★★
<b>BÖHLER K497</b> <b>MICROCLEAN</b>	★★★★★	★★★★★	★★★	★★★★★	★★★★★
<b>BÖHLER K890</b> <b>MICROCLEAN</b>	★★★★	★★★★★	★★★★★	★★★	★★★

**Delivery condition**

**Annealed**

Hardness (HB)	max. 280
---------------	----------

**Heat treatment**


**Stress relieving**

Temperature	650 to 700 °C   1,202 to 1,292 °F	After through heating, hold in neutral atmosphere for 1-2 hours.    Slow cooling in furnace    Intended to relieve stresses caused by extensive machining or in complex shapes.
-------------	-----------------------------------	---

**Hardening and Tempering**

Temperature	1,070 to 1,120 °C   1,958 to 2,048 °F	Quenching: Oil, gas (N <sub>2</sub> )    Holding time after temperature equalization: 20-30 minutes (hardening temperature 1070 to 1100 °C   1958 to 2012 °F) or 10 minutes (hardening temperature 1120 °C (2048 °F)    After hardening, tempering to the desired working hardness according to the tempering chart.
-------------	---------------------------------------	--

**Tempering Chart**

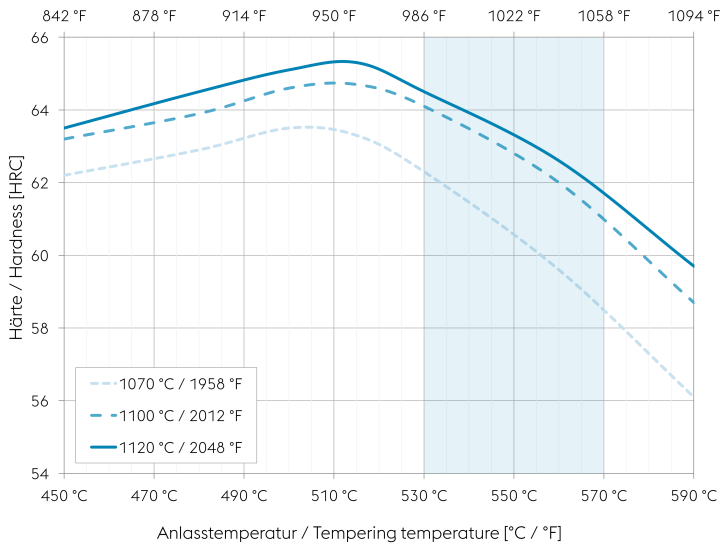

Slow heating to tempering temperature immediately after hardening.

Time in furnace 1 hour for each 20 mm (0,787 inch) of workpiece thickness but at least 2 hours.

Please refer to the tempering chart for guide values for the achievable hardness after tempering.


It is recommended to temper at least three times above the secondary hardness maximum.

Cooling in air to room temperature after each tempering step is recommended.

Tempering for stress relieving 30 to 50 °C (86 to 122 °F) below the highest tempering temperature.

Recommended tempering temperature range is indicated by the blue area in the chart.

**Continuous cooling CCT curves**

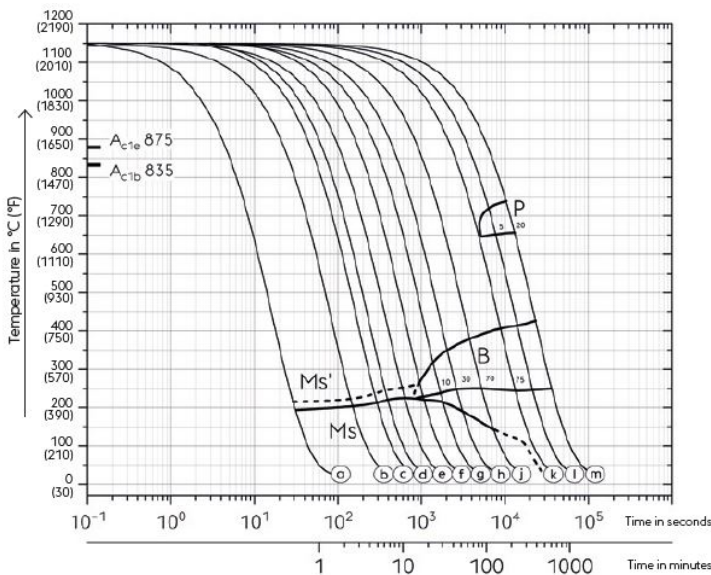

Austenizing temperature: 1150 °C / 2102 °F

Soak time: 180 sec


5...75 Phase proportion in %

0.08...110.00... Quenching parameter λ, i.e. quenching time from 800 to 500 °C (1470 - 930 °F) in s x 10<sup>-2</sup>

P...Perlite  
B...Bainite  
Ms... Martensite starting temperature  
M...Martensite

Sample	λ	HV <sub>10</sub>	Sample	λ	HV <sub>10</sub>
a	0.08	835	g	5.00	800
b	0.40	835	h	8.00	740
c	0.80	840	j	16.00	600
d	1.10	835	k	40.00	540
e	1,80	820	l	65.00	515
f	3.00	820	m	110.00	480

**Quantitative phase diagram**

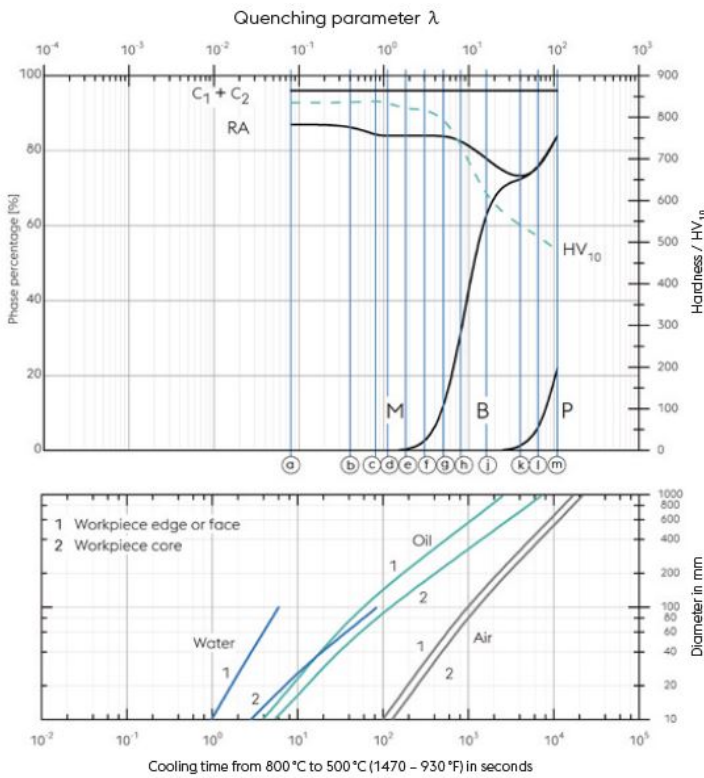

- C1...Carbide content not dissolved during austenitization
- C2...Start of carbide precipitation during quenching from the austenitization temperature
- RA...Retained austenite
- A...Austenite
- M...Martensite
- P...Pearlite
- B...Bainite

**Physical Properties**

<b>Temperature (°C   °F)</b>	<b>20   68</b>
Density (kg/dm <sup>3</sup>   lb/in <sup>3</sup> )	7.86   0.28
Thermal conductivity (W/(m.K)   BTU/ft h °F)	20.8   12.02
Specific heat (kJ/kg K   BTU/lb °F)	0.442   0.1056
Spec. electrical resistance (Ohm.mm <sup>2</sup> /m   10 <sup>-4</sup> Ohm.inch <sup>2</sup> /ft)	0.5   2.36
Modulus of elasticity (10 <sup>3</sup> N/mm <sup>2</sup>   10 <sup>3</sup> ksi)	218   31.62

**Thermal Expansions between 20°C | 68°F and ...**

Temperature (°C   °F)	100   212	200   392	300   572	400   752	500   932	600   1,112	700   1,292
Thermal expansion (10 <sup>-6</sup> m/(m.K)   10 <sup>-6</sup> inch/inch.°F)	10.7   5.9	11.5   6.4	11.9   6.6	12.5   6.9	12.5   6.9	12.8   7.1	12.7   7.1

The data contained in this brochure is merely for general information and therefore shall not be binding on the company. We may be bound only through a contract explicitly stipulating such data as binding. Measurement data are laboratory values and can deviate from practical analyses. The manufacture of our products does not involve the use of substances detrimental to health or to the ozone layer.

**voestalpine BÖHLER Edelstahl GmbH & Co KG**  
 Mariazeller Straße 25  
 8605 Kapfenberg, AT  
 T. +43/50304/20-0  
 E. info@boehler-edelstahl.at  
<https://www.voestalpine.com/boehler-edelstahl/de/>

**voestalpine**  
ONE STEP AHEAD.